



# Structural Integrity Technologies Inc.

80 Esna Park Drive, Units 7-9, Markham, Ontario, L3R 2R7, Canada  
Tel: +1-416-917-1519; Fax: +1-905-415-3633; website: [www.sintec.ca](http://www.sintec.ca); e-mail: [info@sintec.ca](mailto:info@sintec.ca)

## Ultrasonic Impact Treatment (UIT/UP) of Parts and Welded Elements

Intense levels of high frequency acoustic energy or high power ultrasonic (HPU) have found practical use in many industrial processes, of which cleaning, welding and drilling are well-known examples. In most industrial applications, HPU involves power levels of hundreds to thousands of watts, and ultrasonic systems are operating in the frequency ranges from 15 kHz to 100 kHz. Typical amplitudes range from about 10 to 40 microns. Such ultrasonic system operating at 20-25 kHz is creating a cyclic acceleration of around 50,000 g (acceleration of gravity).

One of the promising directions in using of the HPU for industrial applications is the Ultrasonic Impact Treatment (UIT) of parts and welded elements. In most industrial applications the UIT is known as Ultrasonic Peening (UP). The UIT/UP produces a number of beneficial effects in metals and alloys. Foremost among these is increasing the resistance of materials to surface-related failures, such as fatigue, fretting fatigue, stress corrosion cracking and wear.




Basic UP system for fatigue life improvement of parts and welded elements

## Structural Integrity Technologies Inc.

The UP technique is based on the combined effect of high frequency impacts of special strikers and ultrasonic oscillations in treated material. The developed system for UP includes an ultrasonic transducer, generator and a laptop (optional item) with software for UP optimum application - maximum possible increase in fatigue life of welded elements with minimum cost, labor and power consumption.

The beneficial effect of UP is achieved mainly by relieving of harmful tensile residual stresses and introducing compressive residual stresses into surface layers of metals and alloys, decreasing of stress concentration in weld toe zones and enhancement of mechanical properties of the surface layers of the material. The UP treatment is the most efficient technique for increasing the fatigue life of welded elements as compared to such existing improvement treatments as grinding, TIG-dressing, shot peening, hammer peening, etc.

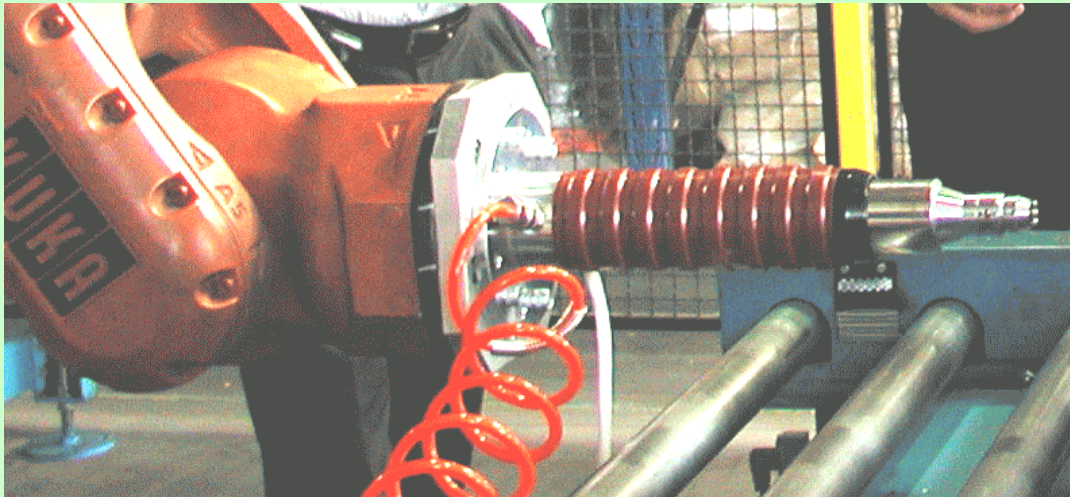


UP system installed on a robot for industrial application

The UIT/UP technology is considered as a leading technology in the application of HPU for fatigue life improvement of parts and welded elements because of the following factors:

1. The UP technology is based on more than 30 years of extensive experience and knowledge of an international group of experts in application of HPU for improvement of quality and service life of parts and welded elements.
2. The design of the UP equipment is based on "Power on Demand" concept. The power and other parameters of UP equipment correspond to the necessary changes in residual stresses, stress concentration and mechanical properties of the surface layers of materials to attain maximum possible increase in fatigue life of welded elements. The basic UP system covers most of the applications in fatigue improvement with the power consumption of 300-500 watts. More powerful UP systems are also designed and produced on request for special applications.

3. The effects of different improvement treatments, including the UP treatment, on the fatigue life of welded elements depend on the mechanical properties of used material, the type of welded joints, parameters of cyclic loading and other factors. For effective application of the UP, depending on the abovementioned factors, a software package for Optimum Application of UP was developed that is based on an original predictive model. In the optimum application, a maximum possible increase in fatigue life of welded elements with minimum time-, labor- and power-consumption is thought.

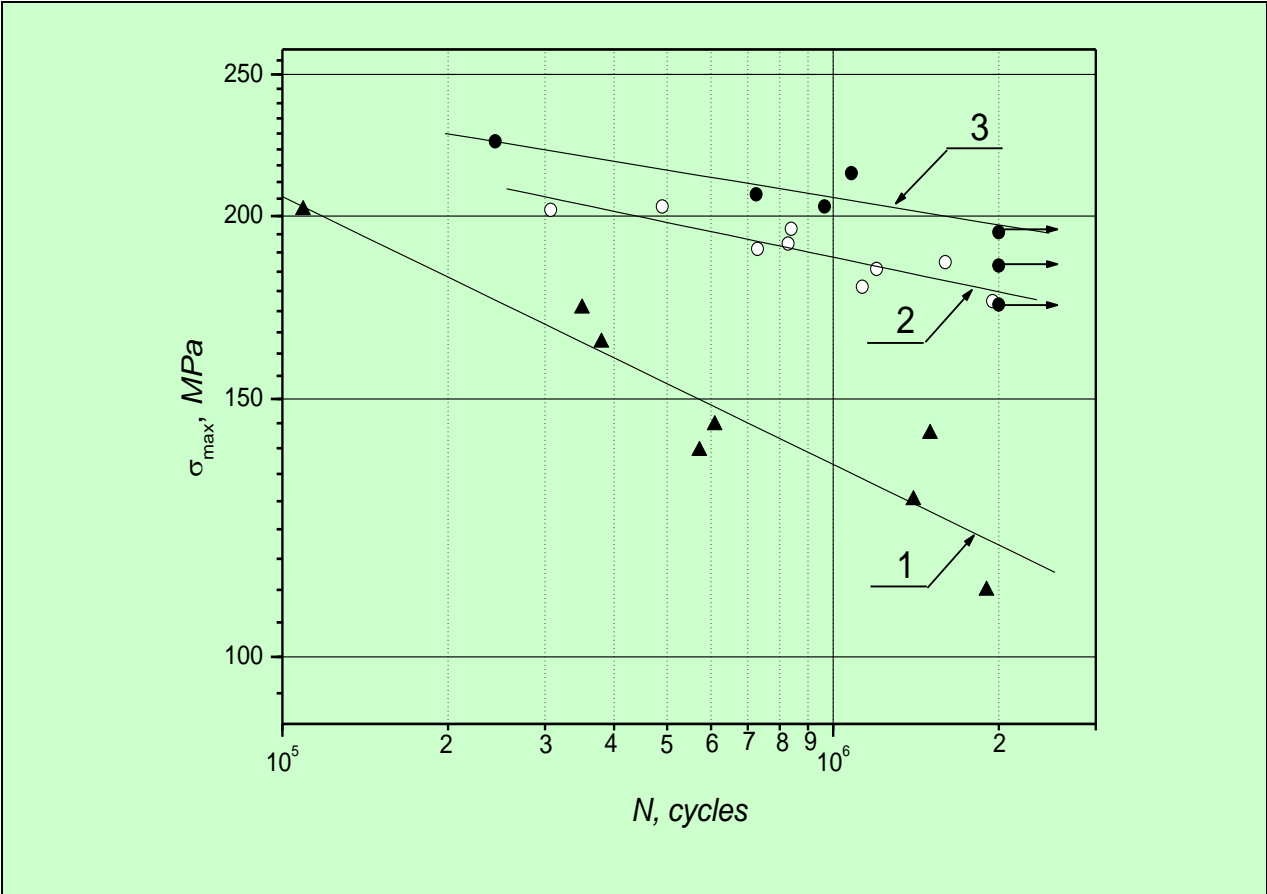


Fatigue curves of large-scale welded samples (transverse non-load-carrying attachment, R=0):  
1 – in as-welded condition, 2 – UP was applied before fatigue testing,  
3 – UP was applied after fatigue loading with the number of cycles corresponding to 50% of expected fatigue life of samples in as-welded condition

One of the examples of effective application of UP is the fatigue life improvement of welded elements of highway and railway bridges. It was shown that UP treatment of about 100 mm of a weld in the end zones of the welded stiffeners leads to a significant increase of the fatigue life of the considered welded element and could eliminate the fatigue crack origination. During the rehabilitation of a highway bridge over Ohio River the total length of UP treated welds was about 500 meters and more than two thousands welded elements that are critical from fatigue point of view were UP treated.

## Structural Integrity Technologies Inc.

The developed computerized complex for UP was successfully applied in different applications for increasing of the fatigue life and corrosion resistance of welded elements, elimination of distortions caused by welding and other technological processes, residual stress relieving, increasing of the hardness of the surface of materials and surface nanocrystallization. The areas/industries where the UP was applied successfully include: Railway and Highway Bridges, Mining, Construction Equipment, Shipbuilding, Automotive and Aerospace.

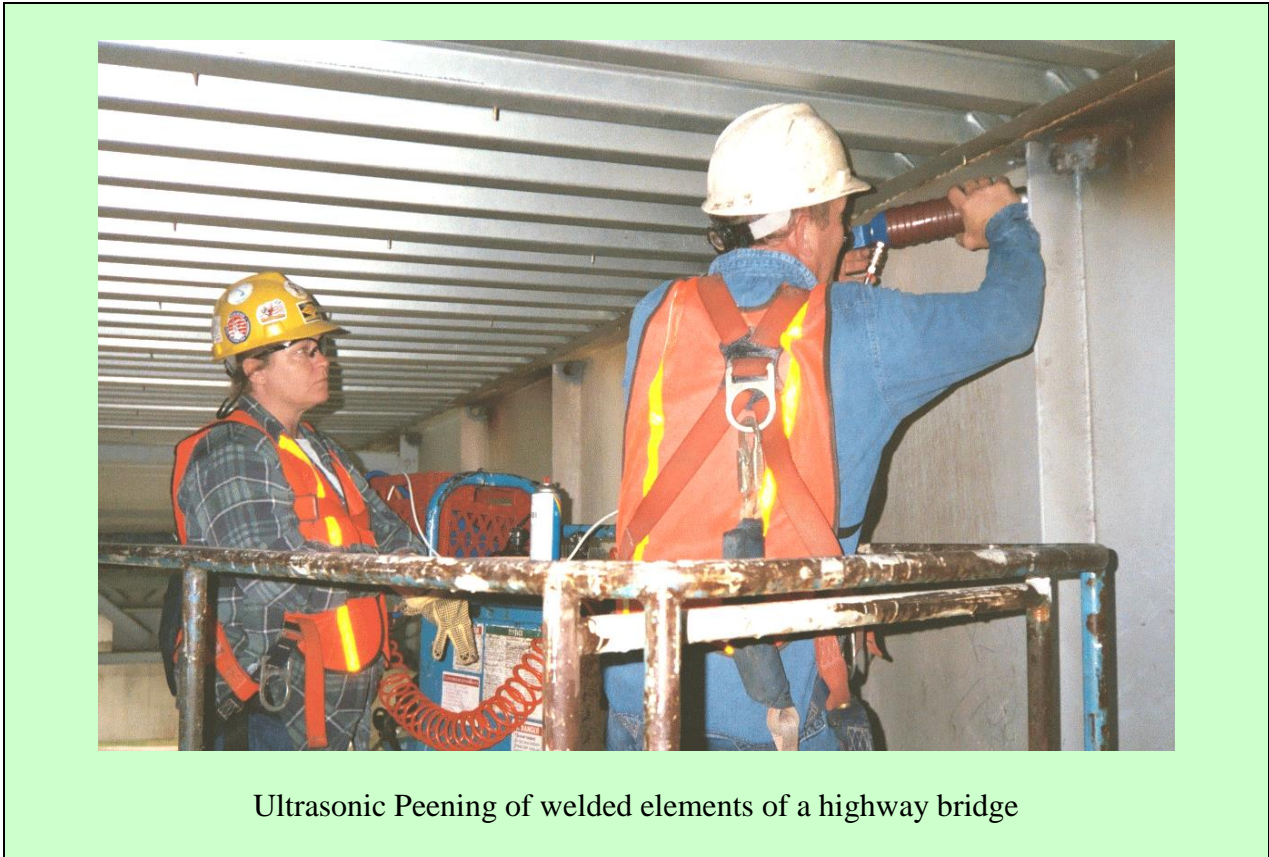

Ultrasonic Peening of welded elements of a highway bridge

### About us

The Structural Integrity Technologies Inc. (SINTEC) is a leading company in the development and industrial application of HPU for fatigue improvement of parts and welded elements. The SINTEC exclusively represents the UIT/UP technology and a number of other ultrasonic technologies in the world market. The SINTEC manufactures and provides the equipment for UIT/UP. The SINTEC cooperates closely with the companies Structural Integrity Services Inc. (SINTES) and Integrity Testing Laboratory Inc. (ITL) with all three companies being members of the Ultrasonic Testing & Technologies (UT&T) Group of companies.

### References

Y. Kudryavtsev. Residual Stress. *Springer Handbook on Experimental Solid Mechanics*. Springer – SEM. 2008. P. 371-387.

**Structural Integrity Technologies Inc.**

Y. Kudryavtsev, V. Korshun and A. Kuzmenko. Improvement of Fatigue Life of Welded Joints by Ultrasonic Impact Treatment. *Paton Welding Journal*. 1989. No. 7. p. 24-28.

Y. Kudryavtsev and J. Kleiman. Fatigue Improvement of Welded Elements and Structures by Ultrasonic Peening. *Proceedings of the ASME 2013 Pressure Vessels and Piping Conference PVP2013*. Paper Number PVP2013-97185. July 14-18, 2013, Paris, France.

Y. Kudryavtsev and J. Kleiman. Increasing Fatigue Strength of Welded Elements and Structures by Ultrasonic Impact Treatment. *International Institute of Welding. IIW Document XIII-2318-10*. 2010.



Final assembly and tuning of UIT/UP systems at SINTEC

Y. Kudryavtsev, J. Kleiman and Y. Iwamura. Fatigue Improvement of HSS Welded Elements by Ultrasonic Peening. *Proceedings of the International Conference on High Strength Steels for Hydropower Plants*, July 20-22, 2009. Takasaki, Japan.

Y. Kudryavtsev and J. Kleiman. Fatigue of Welded Elements: Residual Stresses and Improvement Treatments. *Proceedings of the IIW International Conference on Welding&Materials*. July 1-8, 2007, Dubrovnik, Croatia. P. 255-264.

## Structural Integrity Technologies Inc.

Y. Kudryavtsev, J. Kleiman, A. Lugovskoy et al. Rehabilitation and Repair of Welded Elements and Structures by Ultrasonic Peening. *International Institute of Welding. IIW Document XIII-2076-05. 2005. 13 p.*

Y. Kudryavtsev, J. Kleiman and V. Knysh. Fatigue Strength of Structural Elements with Cracks Repaired by Welding. *International Institute of Welding. IIW Document XIII-2236-08. 2008. 7 p.*

Y. Kudryavtsev and J. Kleiman. Application of Ultrasonic Peening for Fatigue Life Improvement of Automotive Welded Wheels. *International Institute of Welding. IIW Document XIII-2075-05. 2005. 9 p.*

### SINTEC's patents on UIT/UP

Patent of USA # 6467321. 2002. Device for Ultrasonic Peening of Metals.

Patent of USA # 8747732. 2014. Ultrasonic Instrument for the Deformation Treatment of surfaces and Welded Joints.

Patent of Russian Federation # 2540230. 2014.

Patent of Japan # 5779600. 2015.

**For enquiries or demonstration  
please contact us at:**

## Structural Integrity Technologies Inc. (SINTEC)

Phone: (416) 917-1519

Fax: (905) 415-3633

Email: [info@sintec.ca](mailto:info@sintec.ca)

Web site: [www.sintec.ca](http://www.sintec.ca)

Address:

**SINTEC**

80 Esna Park Dr., Units 7-9

Markham, Ontario, L3R 2R7

Canada

